

Review

The Use of Carbon-Containing Compounds to Prepare Functional and Structural Composite Materials: A Review

Elena G. Zemtsova *, Andrey Yu. Arbenin, Yuri V. Sidorov, Nikita F. Morozov, Petr M. Korusenko, Boris N. Semenov and Vladimir M. Smirnov

Institute of Chemistry, St. Petersburg State University, 7/9 Universitetskaya nab.,
199034 Saint Petersburg, Russia

* Correspondence: ezimtsova@yandex.ru

Abstract: The review presents data on the synthesis, properties of carbon-containing compounds, and their application in the technology of obtaining functional and structural composites. Such materials are widely used in recent years due to their good physical and mechanical properties. The review discusses in detail the influence of the chemical composition of various carbon-containing substances and the size of the dispersed phase on the mechanical and physical properties of produced metal matrix composite. The review also concerns methods for the modern synthesis of graphene, carbon nanotubes, and metallic functional and structural composites with reinforcing carbon-containing compounds. Additionally, the results of metal matrix composite modeling are presented. They show that the improved mechanical properties of CNT–Al composites can be attributed to three factors: CNT hardening, matrix grain refinement, and layered architecture.

Keywords: composite materials; functional properties; structural properties; carbon-containing substances; graphene; carbon nanotubes; aluminum

Citation: Zemtsova, E.G.; Arbenin, A.Y.; Sidorov, Y.V.; Morozov, N.F.; Korusenko, P.M.; Semenov, B.N.; Smirnov, V.M. The Use of Carbon-Containing Compounds to Prepare Functional and Structural Composite Materials: A Review. *Appl. Sci.* **2022**, *12*, 9945. <https://doi.org/10.3390/app12199945>

Academic Editor: Mark J. Jackson

Received: 10 August 2022

Accepted: 26 September 2022

Published: 3 October 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

The development of modern technology requires a qualitative improvement in technical characteristics, which can only be achieved if fundamentally new structural and functional materials are created and integrated. Operating conditions put forward extremely stringent requirements for new structural materials, the main of which is to ensure maximum strength and rigidity of structures with minimum weight characteristics. Replacing monolithic traditional materials with composites improves the reliability and weight efficiency of structures [1–5].

Composites based on light metal alloys reinforced with carbon compounds, due to their high anti-friction characteristics in combination with high wear resistance, bearing capacity, damping properties, low specific gravity, and high operating temperatures, are very promising materials for friction pairs of ship structures, helicopters, and oil-producing equipment, rolling mills, and textile machines.

One of the directions of modern industry development is the transition to new functional and structural composites. Progress in the nuclear, aerospace, automotive, energy, semiconductor, transport, and many other technology fields is largely based on the development of methods for obtaining new composites with a nanodispersed phase and improved functional properties [4–12].

For structural materials, operating conditions put forward extremely stringent requirements, the main of which are to ensure maximum strength and rigidity of structures with minimum weight characteristics, maximum impact strength in a wide temperature range, high wear resistance and load-bearing capacity, necessary tribological properties, high fatigue strength, reliability, and long service life when exposed to significant loads.

At the same time, it is important at the present stage to increase the competitive advantages of new structural products that replace traditional metallic materials. These requirements are met by aluminum matrix composites (AMCs) with a carbon-containing based dispersed phase, in which the targeted regulation of the composition and improvement of the methods for manufacturing composites allows reaching a fundamentally new level of performance properties and low cost [4–7].

Carbon nanotubes and nanofibers, which have high mechanical characteristics, are considered effective means of improving the physico-mechanical properties of composite materials (CM). When their surface is functionalized (contains various oxygen-containing groups), carbon nanomaterials have free chemical bonds; therefore, they can provide better adhesion between the matrix and filler and, as a result, increase the strength of the material.

An effective way to further improve the service properties of CMs (high-temperature strength, rigidity, wear resistance, as well as reduce the cost and improve the manufacturability of CMs) can be the synthesis of reinforcing components directly in the manufacturing processes of CMs. Even at a low volume fraction of reinforcing nanotubes and nanofibers for metal matrix composite materials, high strength is found. Due to this, materials for various fields of technology can be made of them [8–10,13–18].

There is a significant reserve for further improvement of the properties of particulate-filled composites through the development of nanotechnologies and the implementation of the principles of transformation hardening, which are especially effective for heterophase systems, which include composites: the development of methods for introducing reinforcing components of various nature, volume content, and size into a metal matrix, including mechanically activated modifying nanophases; creation of hybrid composite due to poly-reinforcement and functional reinforcement; regulation of the matrix alloys composition; the use of ultrafast hardening in order to obtain an amorphous state and the formation of submicrocrystalline structures during subsequent heat treatments [4,5].

An effective way to further improve the service properties of composites—high-temperature strength, rigidity, bearing capacity, and wear resistance—as well as reduce the cost and improve the manufacturability of composites can be the implementation of the synthesis of reinforcing components directly in the manufacturing process of composites. Thus, the improvement of methods for the synthesis of dispersion-filled composites in order to achieve the desired performance properties is an urgent task. Carbon-containing substances (carbon nanotubes, carbon nanofibers, carbides, etc.) are actively used to obtain such composites [13–18]. In particular, actively carbon-containing substances began being used with the development of research in the field of nanostructures and nanostructured materials [10,13–16]. Since the 1990s, works have been published showing that the introduction of carbon-containing nanostructures into a metal matrix in order to strengthen it can significantly improve the properties of composites and expand the scope of their application [17,18].

From the analysis of the scientific literature, we can conclude that, at present, the existing methods for the synthesis of structural composites do not allow for achieving a uniform distribution of the dispersed phase in the bulk metal matrix [3–6]. The lack of a uniform distribution of the dispersed phase prevents the achievement of the maximum effect in the mechanical properties of the resulting structural composite [1–5].

The review analyzes the current state of research in the field of synthesis of carbon-containing materials, as well as composites with a carbon-containing dispersed phase, and their practical application.

The review analyzes the current state of research in the field of synthesis of carbon-containing materials (nanotubes (CNTs), nanofibers (CNFs), graphene), as well as composites with a carbon-containing dispersed phase, and their practical application. With the help of the synthesis methods and models of structure description presented in the review, it is possible to trace the influence of interfacial behavior, the volume fraction of

CNTs, and layered structures on the mechanical behavior of metal matrix composites (MMC) in order to understand the mechanisms of hardening and deformation.

2. Carbon-Containing Compounds: Their Synthesis and Application in the Technology of Obtaining Composite Functional and Structural Materials

To date, various forms of carbon nanostructures are known, including fullerenes, graphene [19,20], carbon nanofibers, carbon filaments, and CNTs [21–24], as well as various carbides [6–10] (Figure 1).

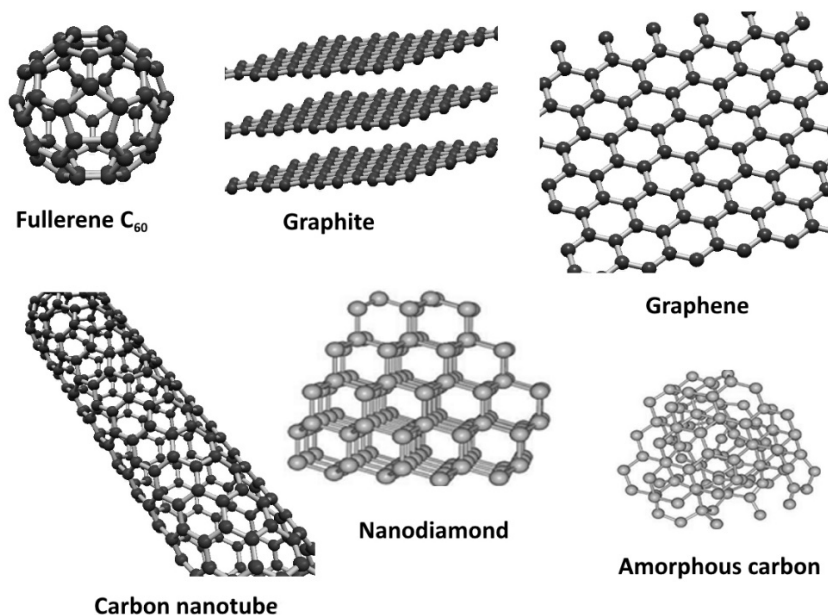


Figure 1. Different forms of nanocarbon.

It should be noted that due to the unique properties of carbon nanostructures (nanotubes, graphene, etc.), namely, high strength, superconductivity, capillary, optical, and magnetic properties, they are used as catalysts; absorbents and shields of electromagnetic waves; as anodes in lithium-ion batteries; as fillers or coatings for composites; nanoprobe; sensors; supercapacitors; electron sources for microscopy [10,23]. Ultrathin films made of single-walled nanotubes can currently become the most suitable basis for electronic sensors. Materials with high tunability and very low microwave loss are currently being sought due to the increasing number of applications requiring such characteristics (mobile phones, remote sensing, global navigation satellite systems, etc.).

Recently, technologies have been developed for the use of carbon-containing compounds as fillers in polymer composite materials for structural applications. They are considered ideal reinforcing materials for polymers and metals [24]. It has been established that the addition of 1% nanotubes by mass to polystyrene increases the elasticity modulus and tensile strength of the material by 42% and 25%, respectively. To obtain effective composite materials with improved tribological properties, various nanosized fillers are also successfully used: carbon fibers, carbon nanotubes, and nanodiamond particles [9]. For example, it was shown in [19] that the addition of carbon nanotubes and nanoparticles to an epoxy matrix leads to a significant decrease in material wear during tribological tests and also leads to multiple (up to 8 times) decreases in the friction coefficient.

2.1. Carbon-Containing Functional Composites Based on Graphene

The active interest in graphene is due to the search for new functional film (2D) materials and technologies based on them, aimed at cost-effective, large-scale production of electronic components and flexible electronics devices [25–30].

Graphene is a single layer of carbon atoms tightly packed in a benzene ring structure. The graphene model is widely used to describe the properties of many carbon-based materials, including graphite, fullerenes, nanotubes, and others [30–33]. An overview of graphene synthesis techniques is shown in the flow chart in Figure 2.

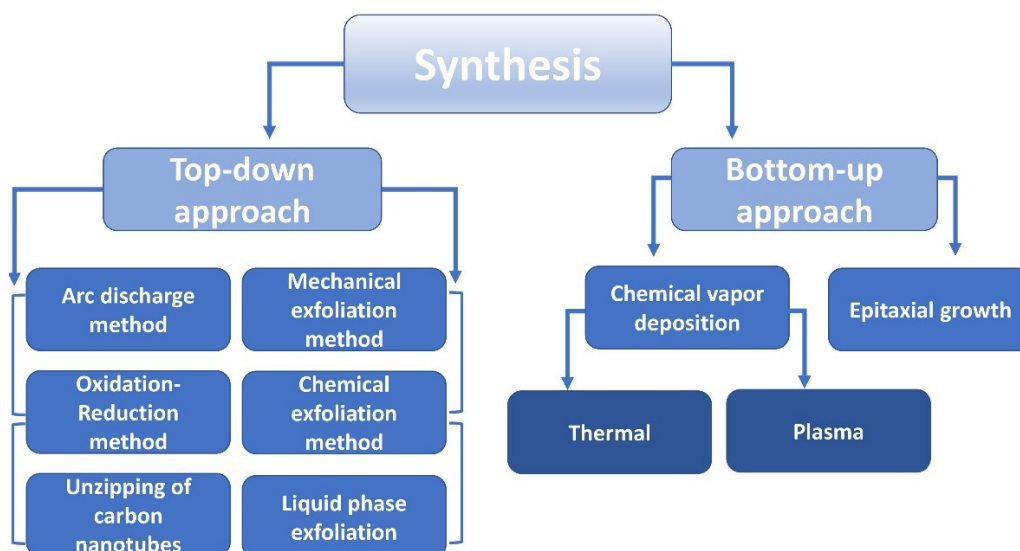


Figure 2. A process flow chart of Graphene synthesis [34].

It was noted [29] that the structure of graphene is responsible for its high specific surface area of $\sim 2630 \text{ m}^2/\text{g}$ and good electrical conductivity.

The mobility of carriers in graphene films at room temperature, which is due to scattering by impurities or nanowaviness of the crystal, has a huge potential for growth and, according to experimental estimates, is limited by the value of $200,000 \text{ cm}^2/\text{W}\cdot\text{s}$ due to phonon scattering [30–35].

Young’s modulus or modulus of elasticity of monolayer graphene membranes is $340 \pm 50 \text{ N/m}$ or $E = 1.0 \pm 0.1 \text{ TPa}$, and the tensile strength of defect-free graphene is determined as $\sigma \sim 42 \text{ N/m}$. Despite its incredible strength, graphene is flexible and can be subjected to 20% deformation without the crystal lattice breaking [36].

For a suspended monolayer graphene “particle” obtained using mechanical separation, the thermal conductivity was about 5000 1/W K [37,38].

For graphene, constant transparency ($\sim 97.7\%$) in the visible range and transmittance that linearly decreases with the number of layers for n -layer graphene were experimentally found [39]. Opacity increases with graphene thickness so that each graphene layer adds 2.3% [40–43]. In [44], the authors were able to solve the problem of the instability of two-dimensional crystals and the isolation of graphene. In this work, the authors experimentally obtained graphene by the mechanical splitting of graphite and investigated its unique properties. The production of highly oriented pyrolytic graphite (HOPG) requires temperatures of about 3300 K , while the splitting onto a substrate is carried out at a temperature an order of magnitude lower than the growth temperature; therefore, two-dimensional graphene films are obtained stable [32,45].

In addition, the large specific surface area of 2D materials motivates their use in surface-active applications such as catalysis and sensing. The atomic thickness and high anisotropy provide 2D materials with excellent mechanical flexibility and optical

transparency, which provide great opportunities for the development of 2D materials-based opto-electronic devices and wearable flexible devices [46,47]. It should be noted that during the synthesis of 2D materials, the formation of van der Waals heterostructures is assumed, in which different 2D layers with a strong covalent bond in the plane are transferred to each other, and in the vertical direction, the layers are held by rather weak van der Waals forces [39].

Nonlinear characteristics at room temperature make these structures interesting for practical applications. Since 2013 works began to appear on heterostructures using layers of transition metal dichalcogenides (NbSe₂, MoS₂, WS₂, WSe₂, TaS₂, etc.) [20,29,48,49] (Figure 3). At present, several types of such heterostructures have been created and studied, and they have already shown a huge potential for the development of this direction [29]. A new version of the lateral transistor was proposed using a tunnel-transparent barrier built into a planar graphene channel [48,50,51].

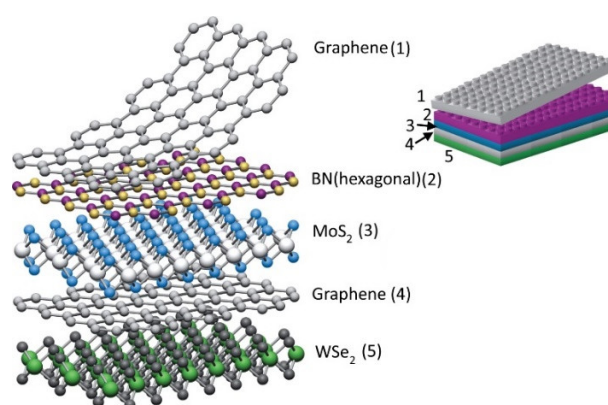


Figure 3. Layer-by-layer formation of a heterostructure based on graphene and other two-dimensional materials. Adapted by permission from Springer Nature [20], copyright © 2022.

Graphene can be considered a molecule that can be chemically modified to obtain a new material with different chemical compositions and interesting properties [52,53].

Depending on the environment, the electronic configuration of the carbon atom (which has four valence electrons) can change significantly, allowing it to bond with other atoms. The combination of carbon atoms with oxygen forms graphene oxide (GO), which can be characterized as a single monolayer of graphite with randomly distributed sp² and sp³ regions containing hydroxyl (–OH), epoxy (=O), carbonyl (–C=O), and carboxyl (–COOH) functional groups. The chemical composition and heterogeneity of GO are still widely discussed [52,54] (Figure 4).

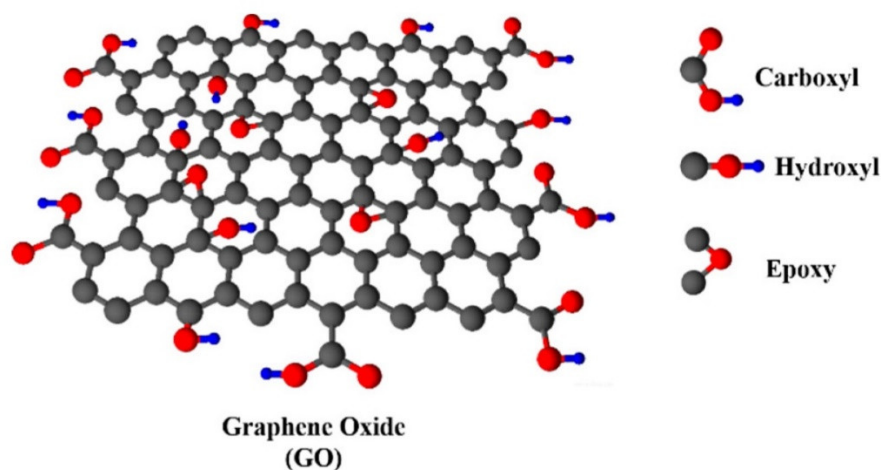


Figure 4. Structure of GO [54].

The optical, electrical, and mechanical properties of graphene are ideal for creating micro- and nanomechanical systems, transparent and conductive electrodes, and photonics. The chemical modification of graphene leads to materials with a wide range of functional properties, which depend on the type of modification and the degree of functionalization [55]. The synthesis of graphene and chemically modified graphene with various degrees of functionalization makes it possible to create a wide range of new materials that can be used in the rapidly developing field of printed electronics [25,26].

Next, we consider the features of using carbon compounds to obtain structural composite materials without considering graphene, which is practically not used in the production of structural materials.

2.2. Carbon Nanotubes and Nanofibers Are Promising Solids for the Preparation of Structural Composite Materials with a Metal Matrix

Currently, CNFs and CNTs are attracting a lot of attention not only because of their structural features and unique physical and mechanical properties but also because of their potential technological applications. The use of CNFs and CNTs can be divided into two groups: (i) the first group includes materials using ensembles of carbon nanostructures, such as composite materials (where CNTs and CNFs are used as reinforcing elements), materials for chemical power sources, adsorbents, catalysts, etc. Note that composites containing CNT/CNF have better mechanical properties [6]; (ii) the second group includes materials using individual CNTs due to their high mechanical and electrical properties [7].

CNTs and CNFs can be used to produce both structural and electrically conductive composites [55]. Due to their unique physical and chemical properties, even small additions of CNTs and CNFs to various materials can significantly improve their mechanical and electrical characteristics. Since the 1990s, works have been published suggesting the introduction of carbon nanostructures into a metal matrix in order to strengthen it, which has significantly improved the properties of composite materials and expanded their scope [56–64]. Theoretical and experimental studies of the mechanical properties of single-walled carbon nanotubes (SWCNTs) are described in many works [5,62,65,66]. The value of the elasticity modulus of SWCNTs and double-walled CNTs (DWCNTs) has a wide range, from 80 to 140 and 140 to 190 GPa, respectively (Figure 5) [67]. Subsequently, the mechanical properties of CNTs were repeatedly confirmed [68]. Destruction experiments were carried out on SWCNT bundles [65]. The average tensile strength was 30 GPa with a range of values from 13 to 50 GPa. It was found that the load led to bundle separation, while the inner tubes of the bundle did not collapse but slipped relative to the outer tubes, which were subjected to destruction. In the case of MWCNTs, it was found that the elastic modulus average value of ~1200 GPa [69]. The strength parameters varied from 20 to 90 GPa [70].

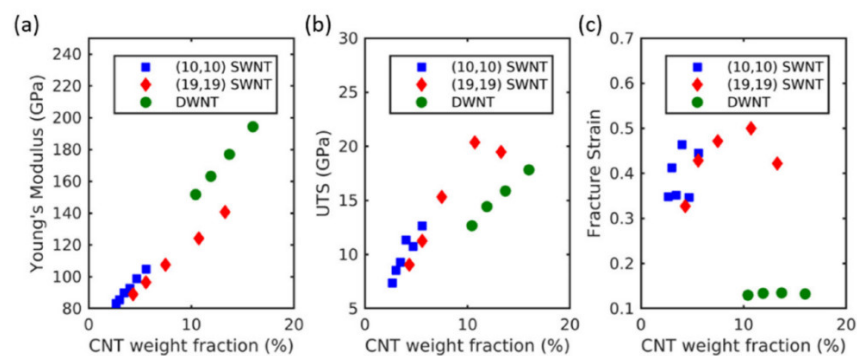


Figure 5. Improvement in mechanical properties of CNT–Al composites as a function of CNT weight fraction: (a) Young’s modulus; (b) ultimate tensile strength; (c) fracture strain. Key for abbreviations: single-wall carbon nanotube (SWNT), double-wall carbon nanotube (DWNT) [67].

From the point of view of practical use, low-density values are extremely important: $\sim 1.4 \text{ g/cm}^3$ for SWCNTs and $\sim 1.8 \text{ g/cm}^3$ for MWCNTs. High heating rates (up to 1000 K/min) reduce the sintering duration, which makes it possible to limit grain growth, and in the case of metal–MWCNT systems, it becomes possible to limit the formation of an undesirable carbide phase during consolidation [71,72].

The value of the specific strength of CNTs is much higher than that of all known materials [22]. As a result, the thermal conductivity of some SWCNTs is very high [73]. The thermal conductivity coefficient obtained by calculation at 400 K is $2.7 \text{ kW/(m}\cdot\text{K)}$. This value approaches the thermal conductivity of nanodiamond film ($2.2 \text{ kW/(m}\cdot\text{K)}$) at 310 K [74]. At ambient temperature, the thermal conductivity of nanotubes is below these values, but nevertheless, it is greater than the thermal conductivity of diamond and is equal to $6.6 \text{ kW/(m}\cdot\text{K)}$. The thermal conductivity of MWCNT measured at room temperature exceeded $3 \text{ kW/(m}\cdot\text{K)}$, i.e., it has an order of magnitude close to that of diamond, but only in the direction corresponding to the tube axis [75,76]. The experimentally obtained values of the thermal conductivity of CNTs are noticeably lower than the calculated values: at normal ambient temperature, along the axis of parallel SWCNTs, they exceed $200 \text{ W/(m}\cdot\text{K)}$, which is approximately equal to the thermal conductivity of metals. For materials with randomly arranged CNTs, this coefficient is an order of magnitude lower [22].

The current density of SWCNTs can theoretically reach 10^9 A/cm^2 (according to some data, even 10^{13} A/cm^2), which is orders of magnitude higher than that of known conductors and superconductors. Additionally, the experimentally obtained values of the current density of MWCNTs without defects— 10^7 A/cm^2 when using contacts made of Au and Ga— $2 \cdot 10^8 \text{ A/cm}^2$. The electrical conductivity of MWCNTs depends mainly on the properties of their outer layer [77].

2.3. Basic Methods for the Synthesis of Carbon Nanotubes

The main modern methods for the synthesis of CNTs are the discharge arc method and methods of deposition from liquid or gaseous media using organometallic catalysts [78,79]. In the discharge-arc method, carbon particles are removed from the graphite electrode in an inert gas flow in an arc discharge plasma and deposited in the form of honeycomb structures on the cathode surface. In this case, mainly MWCNTs are obtained. The method of deposition of CNTs from liquid media (for example, acetone, alcohol) is the decomposition of a mixture of a carbon-containing compound and a catalyst (iron acetates, cobalt acetates) in an argon flow at temperatures of $600\text{--}800 \text{ }^\circ\text{C}$. It is possible to obtain SWCNTs in the resulting soot with a low yield. When obtaining nanotubes from the vapor phase (CVD method), a hydrocarbon (methane, ethylene, acetylene) is passed over a metal-containing catalyst at temperatures of $500\text{--}800 \text{ }^\circ\text{C}$. The method is widely used but has several drawbacks, including the need to maintain high temperatures, as well as the low yield of nanotubes. One of the most promising methods for the formation of structures with a developed surface morphology is metalorganic chemical vapor deposition (MOCVD) using volatile organometallic compounds (metallocenes) and hydrocarbon precursors [80,81]. The use of this method makes it possible to avoid catalyst passivation and makes the pyrolysis process almost continuous. In the world, among the variety of methods for synthesizing CNTs, the MOCVD technology is the most widespread [82,83].

An important stage in the control of chemical properties is the CNTs' functionalization. In composites and other systems, an important role is played by the uniform distribution of nanotubes over the matrix bulk. The high tendency of nanotubes to form clusters, so-called agglomerations, containing up to several hundred CNTs, creates significant difficulties in their dispersion into the material matrix. CNT agglomerations can take the form of a bundle, a bundle, a coiled ball, and so on [22]. Most of the works on the preparation of composite materials with polymer [84,85], metal [86–91], and ceramic [92,93] matrices contain results confirming the expediency of the decision to apply additional processing (functionalization) of CNTs for the purpose of chemical grafting of polar groups to the surface. This treatment makes it possible to obtain a more stable dispersion medium

in polar solvents, increase the chemical activity of the surface, and increase the bond with the matrix [21,94]. The most common are oxidative functionalization methods with the formation of oxygen-containing groups covalently bonded to the CNT surface—carboxyl, hydroxyl, aldehyde, ether, ketone, anhydride, lactone (–OH, –C=O, –COOH) [21,86,94–99]. At the same time, functionalization by oxidation often leads to a decrease in some of the tubes: a decrease in their diameter and length, opening of the ends, and to the appearance of carboxylated fragments on the side surfaces. Thus, their high physical and mechanical characteristics, low density, and nanosized particles make CNTs a promising reinforcing component.

3. Advantages of Composites over Traditional Materials

The main advantages of dispersion-strengthened composites over traditional materials include the optimal combination of strength and ductility, high wear resistance, and satisfactory manufacturability [100,101]. The materials combine valuable mechanical properties with the required operational properties and have a density 2.5 and 3 times lower than steel and bronze. As a result, the formation of a set of properties that is as close as possible to the required one is ensured, as well as the possibility of manufacturing both structurally homogeneous isotropic parts and functionally reinforced and layered compositions. The use of composite materials ensures the reliability of the structure during operation, weight loss, and a significant reduction in the cost of products. In modern technology, the simultaneous development of fundamental sciences, technical disciplines, and tribology has made it possible in practice to create friction units of the highest quality, operating not only in transport and technological machines, but also in extreme conditions, high and low temperatures, in vacuum, with radiation, and in chemically aggressive environments on earth and in space. However, even today, there are problems with creating friction units that are optimal in terms of characteristics, and scientific achievements in this area are far from perfect. The issue of reducing energy consumption for friction and increasing the durability and reliability of tribocouples is very acute [102–104]. In this connection, work on the creation of fundamentally new antifriction materials with a heterophase structure, including metal composites, in which highly plastic metal matrices and refractory high-strength high-modulus fillers are artificially combined, is becoming important. The advantages of aluminum alloys as composite matrices are high thermal conductivity, heat capacity, high technological properties, and lightness. Aluminum-based alloys are three times lighter than copper-based alloys. The addition of particles does not significantly increase the mass, strength, fracture toughness, and load-bearing capacity of the material. The particles of carbon nanotubes and silicon carbide are chemically stable in the aluminum matrix and effectively inhibit the movement of dislocations, thereby increasing the strength of the alloys and slightly changing their specific gravity. Composite systems “aluminum alloys-ceramic particles” have 2–3 times lower density than bronze, have an optimal combination of strength and ductility and have sufficient corrosion resistance. They combine high wear resistance with the required operational and mechanical properties [102,103,105–107]. Reinforcing fillers with a hardness that differs sharply from the matrix not only increases the wear resistance of the composite but acts as supporting supports, reducing the friction coefficients in a wide range of loading parameters [105,106]. The combination of a plastic matrix and high-strength fillers suggests a significant increase in the bearing capacity of bearing materials and an extension of the temperature ranges of work [106]. Good casting properties, cutting capabilities, and weldability characterize the manufacturability of dispersion-hardened composites based on aluminum alloys. The attractiveness of the material is increased by the possibility of varying mechanical properties by choosing alloying systems and modes of subsequent thermal and thermomechanical treatments. One of the distinguishing features is the possibility of creating composite surfaces on substrates of different materials. The most important advantage of composites is the ability to create structures with predetermined properties that most fully meet the nature and conditions of work.

The Influence of Interfacial Interaction of Components in Carbon-Containing Composites on Their Physical and Mechanical Properties

The interfacial interaction of the composite components sets its physical and mechanical properties: strength, hardness, fracture toughness, heat resistance, and others. When controlling the process of interfacial interaction for composites, one should consider the conditions for the compatibility of components and the stability of the interface between phases [103,105,108,109]. When obtaining composites, where fibers are used as a hardener, the interfacial interaction must be limited since intense interaction leads to a deterioration in the final physical and mechanical properties. At high temperatures, chemical reactions can occur at the composite interface. Under the condition that a chemical reaction occurs on the surface, the bond between the reinforcing component and the matrix becomes stronger. However, if the layer is thicker, the reaction products can, on the contrary, weaken the bond, up to the destruction of the fiber. Chemical interaction can occur both during the composites' preparation and during their high-temperature treatment [63,104,106]. From the point of view of boundary processes, there are three classes of fibrous composite materials [4,5]; when the matrix and fiber: (i) are not mutually reactive and soluble, that is, they do not form solid solutions and chemical compounds; (ii) are not mutually reactive, but soluble, then they form solid solutions, but do not form chemical compounds; (iii) react with the formation of a chemical compound at the interface. Changes in the chemical composition occur at the phase boundary. The main task of the interface is to ensure the connection between the matrix and the hardener. Thus, the mechanical properties of the boundary region are very important, in particular, stability under various loading methods. In this area, the following types of bonding are distinguished [6]:

- (1) Mechanical bonding due to friction forces. Such materials have low strength in transverse tension and longitudinal compression (composites of the first class).
- (2) Bond due to surface tension forces. It is typical for materials formed during wetting and dissolution without a chemical reaction. When wetting, a slight dissolution of the components occurs when the fibers are impregnated with a molten matrix (composites of the first and second classes).
- (3) Reactive bond during a chemical reaction at the interface, which results in the formation of other chemical compounds (composites of the third class).
- (4) Exchange-reaction bond. A kind of reaction bond in which a chemical reaction does not occur simultaneously but in several stages.
- (5) Oxide bond. A kind of reactive bond characteristic of composites reinforced with fibers or oxide particles. In composite materials with metal matrices, bonding is achieved through the formation of spinels at interphase boundaries or through an oxide film through which bonding occurs. The interaction between the metal and SWCNTs can lead to MWCNTs with open ends occurring [109,110].

Contact interaction at the open ends of CNTs occurs due to the strong σ -bonds formation, which can lead to a reaction with the formation of metal carbide. The possibility of a chemical interaction between CNTs and fullerene with metal surfaces was experimentally shown in [108–111]. The calculations showed that the binding energy of an Al atom with an ideal surface of an unmodified SWCNT did not exceed 0.4 kJ/mol or $4 \cdot 10^{-3}$ eV due to weak π -bonds. The presence of oxygen-containing functional groups on the CNT surface has a significant effect on the interaction with some metal atoms [108,109]. Firstly, metals create a covalent bond with oxygen, and secondly, groups containing oxygen create conditions for the convergence of the energies of the valence orbitals of metal and CNT atoms, contributing to their greater overlap. The interaction between an Al atom and an SWCNT is due to the formation of a covalent bond with the carboxyl functional group and directly with the SWCNT surface [112]. In practice, the surface of nanotubes is not ideal; therefore, depending on the degree of purity of CNTs and the number of defects and grafted functional groups on their surface, the formation of metal carbide is also possible, which occurs due to the substitution of carbon atoms. Variation of the Gibbs free

energy of formation of various carbides (per mole of graphite) depending on temperature. According to the experimental data [113–115], aluminum is practically insoluble in carbon, and the solubility of carbon in aluminum does not exceed 0.02–0.04 wt. %. The main reaction that determines the interaction between carbon structures and Al is the formation of Al_4C_3 carbide. The interactions of amorphous (glassy carbon), quasi-crystalline (carbon fibers), and crystalline (graphite, nanotubes) carbon structure with Al [116,117] showed that aluminum carbide is formed at 970–1370 K at the time of isothermal contact of carbon materials with liquid aluminum for three or more minutes. When obtaining composites with dispersed or fiber hardeners, the main tasks are to achieve a uniform distribution of the hardener in the matrix and the formation of strong contact at the interface between the phases of the components. At present, there are many methods for obtaining composites based on a metal matrix with an arming component in the form of CNTs (MM-CNT): melt processing (casting, melt infiltration), gasothermal spraying (plasma spraying, cold spraying), electrochemical, (electro- and chemical deposition) new methods (powders mixing at the molecular level, nanoscale dispersion, sandwich processing, laser deposition), etc. (Figure 6). However, the most accessible and widely used methods for obtaining metal matrix composites reinforced with MWCNTs are solid-phase methods of powder metallurgy (PM) [88,104,118,119]. A typical technological process of the PM method consists of the mixing of components and their consolidation. Mixing is usually carried out using mechanical alloying in mills of various types or ultrasonic processing of components in liquid media [61]. Consolidation methods based on the sintering of metal powders can be divided as follows: (i)-conventional sintering, (ii)-hot pressing. The use of this technological scheme, as a rule, leads to a chaotic arrangement of MWCNTs.

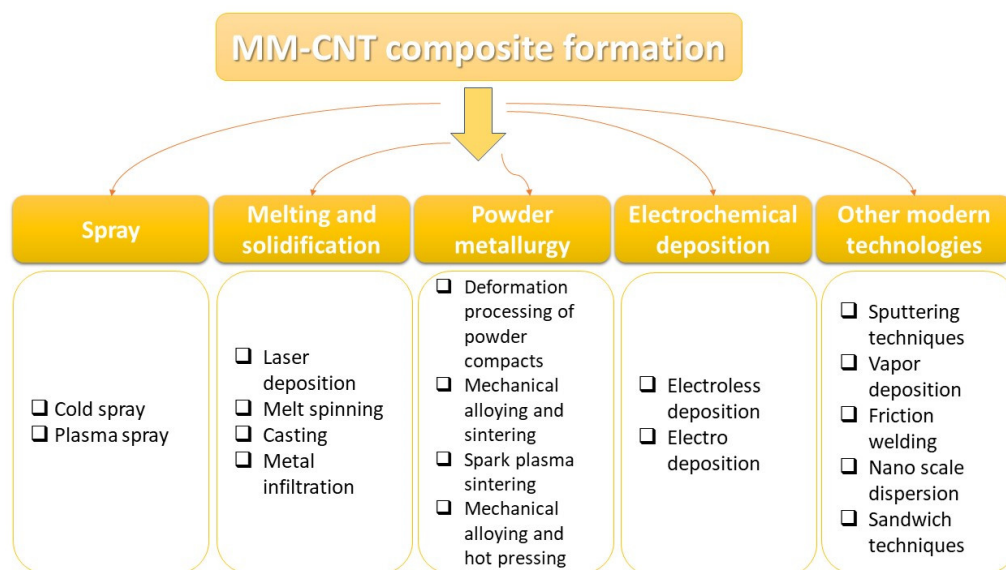


Figure 6. List of different processing routes for MM–CNT composites [5].

In [120,121], MWCNTs were grown on Al powder (Ni catalyst). The resulting powder was pressed at 600 MPa, sintered at 640 °C for 2 h, and additional pressing at 2 GPa was carried out to achieve the required density and properties. Microhardness increased from 0.15 GPa to 0.65 GPa and tensile strength from 140 MPa to 398 MPa. It is also reported that the high increase in strength is associated with a strong interfacial bond in the form of a thin layer of Al_4C_3 between the components (Figure 7). Ag-based composites reinforced with MWCNTs were prepared by mixing powders in a mortar and compaction at 320 MPa, followed by sintering at 700 °C for 1 h [122]. In order to increase the adhesive bond with the matrix, the MWCNTs were treated with acid to roughen the surface. Due to insufficient density after sintering, the composites were pressed again at 400 MPa for further compaction. The authors stated that the uniform dispersion of MWCNTs without the

formation of any clusters was achieved up to 8 vol. % MWCNTs in the composite after sintering at 700 °C [122]. Most studies on sintered metal MWCNT composites indicate insufficient density, which can be increased by reducing the particle size of the matrix powder, improving the uniformity of the distribution of nanotubes, or using additional deformation treatments [89]. In hot pressing, powder mixtures or cold pressed compacts are processed at high temperatures in a mold in a protective environment. Under the combined influence of temperature and pressure, the material is easily deformed, which contributes to the achievement of high density. Al–MWCNT composites were prepared by hot pressing powder mixtures at 520 °C and 25 MPa [118] with a holding time of more than 30 min. The authors of [123,124] obtained Al–MWCNT composites by ball-milling raw materials for different lengths of time. The Al particle size was $\sim 13\ \mu\text{m}$, that of MWCNTs was $l\sim 5\ \mu\text{m}$, and $d\sim 10\text{--}20\ \text{nm}$. Subsequently, the mixture was subjected to hot pressing at 560 °C. It is shown that with an increase in the milling time, the degree of damage to MWCNTs increased, which was noted by an increase in the intensity of the Al_4C_3 phase. Tensile strength and yield strength for the composite Al-0.5 wt. % CNTs (6 h grinding), compared with pure Al, amounted to 42.3% and 18.4%, respectively. Hot pressing has the advantage of producing high-density (>95%) metal–MWCNT composites. The hot-pressing time to achieve the optimal density in most studies was $\sim 1\ \text{h}$. Long-term temperature exposure can lead to metal carbide formation, depending on the quality of the MWCNTs used. Some of these studies have found a reaction between MWCNTs and metal [124,125], while others have followed the stability of MWCNTs. At present, an effective method of consolidation is spark plasma sintering (SPS), the basic principle of which is to heat the powder material by passing a pulsed current with simultaneous application of pressure [126–128].

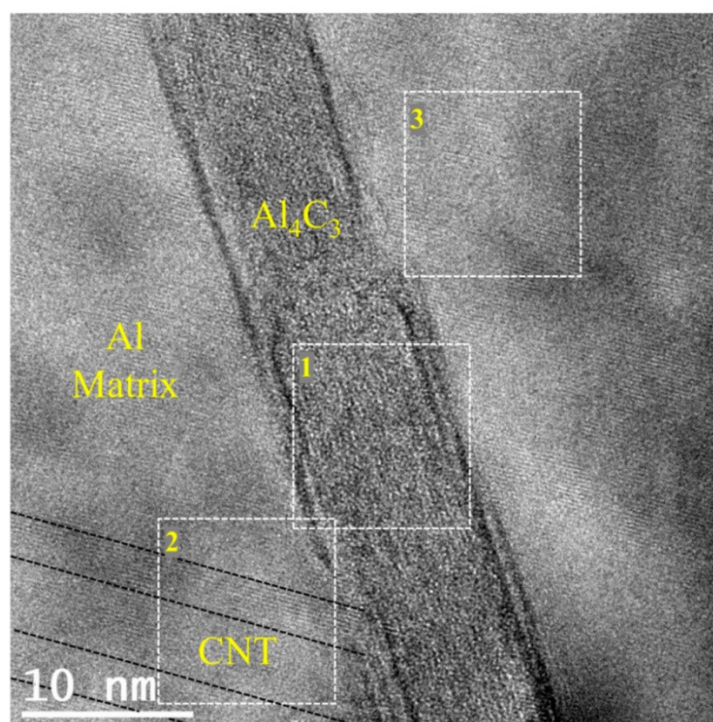


Figure 7. HRTEM image and inverse FFT showing the Al_4C_3 and CNT embedded in the Al matrix [129].

Another paper [129] provides a general view of the strengthening mechanisms of Al–CNT nanocomposites fabricated using 1 vol. % CNT using the powder metallurgy method using the ultrasonic treatment and its combination with a ball mill (Figure 7). It is shown that this approach results in the formation of a homogeneous dispersion of CNTs with

minimal damage. In addition, Al_4C_3 was found, which formed during the preparation of composites; Al_4C_3 plays an important role in transferring the load from the matrix to the reinforcement. As a result, the authors showed that the presence of Al_4C_3 , CNTs, and a high density of dislocations near the latter is the key to improving the mechanical properties of nanocomposites.

Carbon nanofibers and nanotubes are attracting a lot of attention not only because of their structural features and unique physical and mechanical properties but also because of their potential technological applications. In general, the use of CNFs and CNTs can be divided into two groups. The first group includes materials using ensembles of carbon nanostructures, such as composite materials (where CNTs and CNFs are used as reinforcing elements), materials for chemical power sources, adsorbents, catalysts, etc. Note that composites containing CNT/CNF have the best strength-to-weight properties among other materials [84,130]. The second group includes the use of individual CNTs due to their high mechanical and electrical properties [84,130].

Table 1 shows that the properties of MWCNTs are slightly lower than those of SWCNTs since destruction will begin with the outer, defective layer.

Table 1. Mechanical properties of carbon materials [84,130].

Characteristic	Graphite	Carbon Fibers	MWCNTs	SWCNTs	Steel
Tensile strength, GPa	100	3–7	300–600	300–1500	0.4
Modulus of elasticity, GPa	1000	200–800	500–1000	1000–5000	2000
Maximum tensile elongation, %	10	1–3	20–40	20–40	26

There are much fewer studies aimed at reinforcing the ceramic matrix of CNTs, and metal–CNT composites have been little studied.

In addition, the works [131–135] showed the successful reinforcement of the aluminum matrix with carbon nanostructures to improve the tribological characteristics of the composite material. According to [133], the greatest effect in reducing the friction coefficient and wear rate is observed in aluminum alloys reinforced with C_{60} fullerenes and graphite. In [134], a study was conducted on the effect of the concentration of carbon nanotubes in the composition of the aluminum matrix on the wear resistance of the material (Figure 8). The authors showed that wear resistance is effective when the CNT content is less than 2% by weight in the composition of the aluminum matrix. In this case, the best value of wear resistance was obtained for a material with a CNT content of 0.05 wt.%. On the other hand, the simultaneous introduction of two carbon nanostructures of graphene and nanotubes can also lead to a decrease in the degree of wear depending on the sliding speed [135]. In doing so, the authors have shown that the graphene–MWCNT combination is a favorable tribological application compared to individual MWCNTs or graphene.

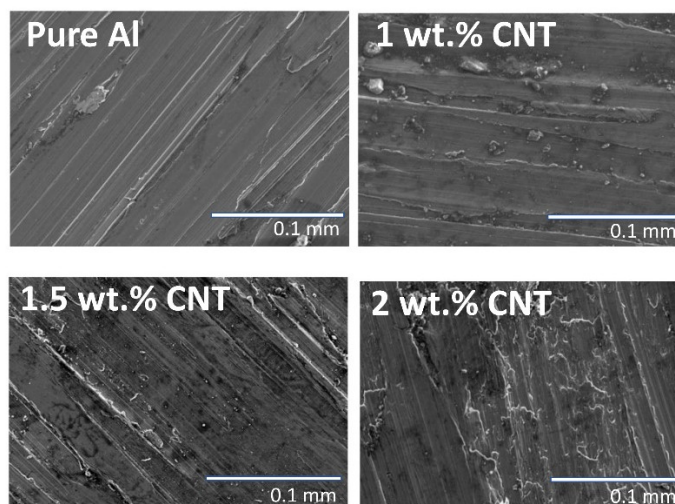


Figure 8. SEM images of the worn surface of pure aluminum alloy and CNT-reinforced aluminum alloy and wear rate data under a load of 2 kg at 500 rpm [134].

4. Modeling of the Hardening of an Aluminum Metal Matrix Composite Reinforced with CNTs

The observed hardening of metal matrix composites is the result of the interaction of several hardening mechanisms:

- (1) Due to the effective transfer of the load between the matrix and the reinforcing elements;
- (2) Due to the internal thermal stresses caused by a mismatch in the coefficients of thermal expansion between the matrix and carbide particles;
- (3) By grinding the grain of the matrix (Hall-Petch law);
- (4) Due to a mismatch between the elastic moduli of the matrix materials and the inclusion;
- (5) Hardening caused by the dispersed phase, according to Orowan;
- (6) Hardening caused by the appearance of an interfacial layer between the reinforcing particle and the matrix.

The mechanisms that are implemented in each particular case are determined both by the geometry, size, and concentration of particles, as well as the conditions for introducing reinforcing particles into the matrix.

The existing methods for modeling the hardening of metal matrix composites can be conditionally divided into two groups:

- Micromechanical modeling based on empirical or semi-empirical models of hardening mechanisms.
- Computer modeling, including modeling by molecular dynamics methods, finite element modeling, and multiscale modeling, representing some combination of molecular dynamics and finite element modeling.

The main problems affecting metal matrix composite hardening are the uneven particle distribution in the bulk, the aggregation of reinforcing particles, and the formation of defects at the particle–matrix interface. One of the important tasks is to prevent these problems [103,136,137].

Unlike macroscale descriptions of hardening mechanisms such as the Hall–Petch or Orowan ratios, where the differential increase in strength associated with a single hardening mechanism is added to the base strength of the material, the microscale considers dislocations to interact directly with various obstacles independently and uses the absolute critical allowed shear stress for each type of obstacle.

Casati R. et al. [62] reviewed the theoretical and experimental foundations related to bulk MMCs and the main results achieved in this area. The structural properties and

mechanical characteristics caused by the addition of nanoparticles and nanotubes to base metals are presented, and modern methods for the synthesis of MMCs are described.

Kun X. et al. [138] studied the mechanisms of MMCs hardening with CNTs-reinforced Al matrix, including load transfer, dispersion strengthening, dislocation formation caused by thermal mismatch, fine-grained hardening, etc., have been studied.

Xu R. et al. [139] developed a microstructure-based work hardening model by modifying and combining the Cox–Mecking approach to dislocation density evolution, reverse stress models for grain boundaries, and reverse stress models for second phases. The expected strain hardening characteristics of the composites were successfully matched with the experimental results. It has been shown that the effects of CNT reinforcement and grain refinement can significantly increase the strength of composites. Authors in [140,141] discussed the formation of coated CNTs (there is an amorphous interfacial surface between the reinforcement and the metal matrix), which have a great influence on the force acting on dislocations. This article proposes a model of a three-phase compound cylinder with new boundary conditions. This model studies the interaction of CNT edge dislocations with a coating containing the interface effect.

Liu Z.Y. et al. [142], using Tsai–Halpin’s equation, showed that with an increase in the concentration of CNTs in MMC, the elastic modulus of composites increases. The tensile strength of composites is significantly increased compared to the matrix alloy, which is explained by the mechanisms of load transfer, grain refinement, and misfit dislocation due to the addition of CNTs. Modifications are proposed to consider the mechanisms of hardening according to Orowan due to the redistribution of the load and the refinement of the grain of the matrix material, as well as the discrepancy between the thermal expansion coefficients. The simulation results are in good agreement with the experimental ones.

Dong S. et al. [143] proposed a dislocation-based model to investigate the synergistic effect arising from the grain size of the matrix and the size of the reinforcement on the strengthening mechanisms of nano/ultrafine-grained CNT-reinforced MMCs. The model based on the three-phase composite material approach is suitable for studying the elasto-plastic stress–strain relationships of MMCs. The overall flow strength of nano/ultrafine grain MMC depends on the grain size of the matrix or CNT, as well as the volume fraction and microstructure of the reinforcement. It is assumed that dislocations formed by a mismatch in the thermal expansion coefficient are redistributed only in a strongly dislocated volume that surrounds a separate inclusion. This zone, as a matrix phase in the calculation model, has a higher strength than the rest of the metal matrix. Therefore, the size of the zone is an additional scale of the microstructure and requires more attention. All these results are explained by the strengthening effect that is caused by thermal expansion mismatch weakening as the grain size of the matrix decreases, which leads to the less pronounced role of reinforcement in the overall response of MMC. The model can provide some insight into the strengthening mechanisms of CNT-reinforced nano/ultrafine-grained MMCs.

Chen B. et al. [144] studied the influence of the length-to-diameter ratio of CNTs on hardening aluminum MMCs. To this end, aluminum samples reinforced with CNTs with different aspect ratios were fabricated by three different powder metallurgy methods. The microstructural study showed that CNTs were uniformly dispersed in materials ranging in aspect ratios from 6.5 to 55. Tensile results showed that CNTs exhibited a strong strengthening effect in composites regardless of their aspect ratios. Post-load studies and quantitative analysis demonstrated a transient hardening mechanism for CNTs that is closely related to the aspect ratio or length of the CNTs. The origin of such a transition has been studied from the point of view of the interaction of dislocation with a CNT under load. These data may provide new insights into the enhancement behavior of CNT-reinforced MMCs [145].

Zhou M.Y. et al. [146] studied the properties of the matrix composite AZ61 reinforced with microscale SiC and CNTs. Ultra-high strength and good ductility (tensile strength:

412 MPa, yield strength: 345 MPa and elongation: 8.0%) were achieved in the AZ61-5SiC-0.5CNTs composite. The greatly improved composite strength is mainly due to the synergistic effects of grain refinement, load transfer, and increased dislocation density in the matrix due to thermal mismatch, while good ductility can mostly be attributed to a weakened base texture.

It is noted that the formation of clusters and damage to CNTs during processing can reduce the strengthening effect of CNTs. The distribution of a part of the CNTs along the grain boundaries leads to a weakening of the strengthening effect of the Orowan mechanisms. The weakening of the base texture due to the addition of hybrid reinforcement favorably affected the ductility; however, the weakening of the base texture also compensated to some extent for the effects of hardening [136].

In [147], Choi B. et al. carried out molecular dynamics (MD) modeling study of the mechanical behavior of an aluminum composite reinforced with CNTs with different diameters. Stress–strain curves under tensile loading were obtained, and variations in the curves were analyzed using MD images, which allow a detailed analysis of the behavior of atoms. It is shown that Young’s modulus and impact strength increased significantly as the reinforcement of CNTs increased.

In [137], Zhou X. et al. studied the mechanical behavior of MMCs reinforced with Ni-coated CNTs by MD simulation. The results show that the Young’s modulus of Ni-coated SWCNT/Mg is obviously larger than that of uncoated SWCNT/Mg. The results also show that the interfacial bonding of an SWCNT–Mg composite can be dramatically increased by adding a Ni coating to improve the wettability of the nanotube surface and the Mg matrix. In addition, the effect of the amount of Ni coating on the interfacial bonding characteristics of SWCNT–Mg composites was studied. In [148], Meguid S.A., by MD method using the LAMMPS software package, CNT pulling tests from a matrix are simulated to determine the effect of various parameters that affect the strength of the interfacial shear of metal matrices reinforced with CNTs. The study focuses on the influence of cell size, cell geometry, and potential features assumed in MD simulations.

In [149], Zhang J.F. et al. estimated the influence of the choice of a representative element, the division of a representative element into finite elements, and the interface layer near inclusions on the deformation curves of the metal composite. It is shown that simplified models can be used in estimation calculations (the calculation error, in this case, is no more than 2%).

In [67], the experimental data for CNT–Al composites were compared with the data of MD and the modified rule of mixtures (see Figure 9). Due to dispersion problems observed in experiments, experimental data are given for CNT volume fractions up to 10%. Experimental data showed a large scatter, as the manufacturing process and distribution of CNTs affected the mechanical properties. However, the MD data are generally consistent with experimental data.

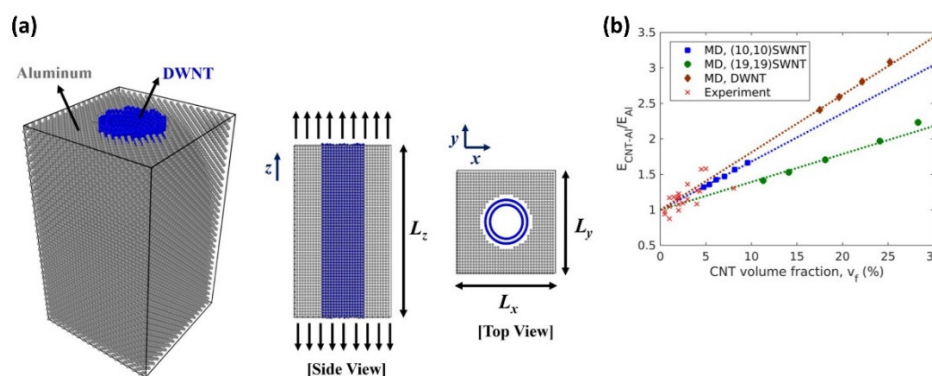


Figure 9. (a) CNT–Al composite in representative volume elements for the MD simulations. $L_z = 124.44 \text{ \AA}$ and $L_z = 97.25 \text{ \AA}$ for DWNT–Al and SWNT–Al, respectively. L_x and L_y were adjusted from

44.5 to 89.1 Å according to the CNT volume fraction and CNT size; (b) the variation of Young's moduli of CNT–Al composites with CNT volume fractions [67].

In [103], Song S. et al. studied the effect of Ni-plated carbon tubes on the strength and deformation properties of a metal composite with an aluminum matrix. It is shown that the main mechanisms of hardening are Orowan dispersion hardening, which is due to the small diameters of CNTs (8 and 15 nm), hardening generated by a mismatch in the coefficients of linear expansion, as well as hardening due to redistribution of the load between the matrix and reinforcing elements. It has been established that the aspect ratio of CNTs plays the most important role in the strengthening of composites in terms of the ratio of length to transverse dimension. Hardening analysis was based both on a micromechanical model and the finite element method.

The review by Jagannatham M. et al. [150] provides an analysis of publications devoted to modeling the properties of metal composites reinforced with CNTs. The sensitivity of the simulated properties to several factors is expected, such as the curvature and orientation of CNTs, the presence of reaction products at the interface, changes in the length of CNTs, etc. To compare the calculated properties with experimental ones, a three-dimensional microstructure of the composite is required, which is impossible due to the small size of CNTs. display using available tomography methods. It is shown that the presence of aluminum carbide Al_4C_3 slightly increases Young's modulus of the composite.

Ahmadi M et al., in [151], and Pérez L. et al., in [152], were to investigate the effect of the Al_4C_3 interfacial surface on the elastic modulus of aluminum matrix nanocomposites reinforced with randomly distributed CNTs using a numerical micromechanical model based on the finite element method (FEM). In addition, the influence of the volume fraction and diameter of CNTs on the elastic modulus of nanocomposites with an aluminum matrix was studied. The results show that the Al_4C_3 interfacial surface significantly affects the elastic modulus of nanocomposites with an aluminum matrix, especially with a decrease in the CNT diameter. With an increase in the thickness of the interfacial boundary, the modulus of elasticity of the nanocomposite increases. The applicability of the presented model for predicting the elastic modulus of CNT-reinforced aluminum-matrix nanocomposites is investigated by comparing the results of the FEM with experimental data available in the literature.

In [153], Dong S. et al. studied the modulus of elasticity and the distribution of local stresses in MMC with a nonrectilinear shape of CNTs using the FEM and a micromechanical model. It is shown that the results of modeling by the finite element method are close to the results obtained based on the micromechanical model and experimental data.

It is concluded that the effect of CNT waviness on the elastic properties of MMCs reinforced with randomly distributed CNTs is small.

The paper by Su Y. et al. [154] attempts to experimentally and numerically investigate the relationship between the microstructure and mechanical behavior of CNT–Al composites. Three-dimensional (3D) computer structural modeling of CNT–Al composites is performed in which the size, morphology, orientation, location, and volume fraction of CNTs are reproduced to be similar to the microstructures of real microstructures of CNT–Al composites.

Based on the developed models of CNT–Al composites, the strengthening of the mechanical properties of the constituent materials of CNT–Al composites, as well as reasonable loads and boundary conditions, is studied. The tensile mechanical behavior of CNT–Al composites has been numerically evaluated and experimentally confirmed. MMC simulation results show that the improved mechanical properties of CNT–Al composites can be attributed to three factors: CNT hardening, matrix grain refinement, and layered architecture. Using the microscopic structural modeling techniques presented here, the influence of model size, interfacial behavior, the volume fraction of CNTs, and layered structures on the mechanical behavior of CNT–Al composites can be reproduced in order to understand the mechanisms of hardening and deformation of CNT–Al composites.

5. Conclusions

In this review, we have tried to summarize information on the synthesis and properties of carbon-containing structures (nanotubes, nanofibers, graphene), as well as on composite materials with carbon inclusions. We reviewed the existing methods for modeling the hardening of metal matrix composites reinforced with carbon structures (nanotubes) in order to understand the mechanisms of hardening and deformation of such systems.

It should be noted that in the traditional synthesis of a composite material, the carbon material used as a dispersed phase must first be synthesized, purified, functionalized, and only then introduced into the matrix. However, even this procedure may not lead to the expected increase in the mechanical properties of the composite due to poor bonding between the carbon substance and the metal. It should be noted that the development of new structural metal reinforced with high-strength dispersed fillers (nanoparticles, nanofibers, tubes) occupies a significant place in the work of researchers. Replacing monolithic traditional materials with composite materials makes it possible to increase the reliability and weight efficiency of structures. Composite materials based on light aluminum alloys reinforced with particles, due to their high antifriction characteristics in combination with low specific gravity and high operating temperatures (up to 0.8–0.9 of the melting temperature of the matrices), are very promising materials.

In this regard, at present, along with the traditional direction of the search for new solid substances and materials (the synthesis of solid substances with an equilibrium crystal structure), the synthesis of solid chemical compounds and materials based on their metastable states is attracting more and more attention.

To improve the mechanical characteristics of carbon composites, researchers are faced with the need to develop new methods for the synthesis of composites with a uniform distribution of nanotubes over the volume of the matrix and ensuring chemical interaction between the filler and the matrix. CNTs in the hydrating composite act as centers or initiators for the crystallization of hydration products, leading to a change in the micro/nanostructure of the matrix, including the pore structure. The high tendency of nanotubes to form agglomerations containing up to several hundred CNTs creates significant difficulties in their dispersion into the material matrix. To solve this problem and reduce the degree of agglomeration, it is necessary to develop new methods for the functionalization of CNTs.

The properties of carbon nanomaterials and the possibility of using them in technological processes are also determined by the structure of their surface layer. In this regard, researchers today face a very difficult task—to develop methods and approaches for directed control of the physicochemical properties of the surface layer of reinforcing carbon nanostructures to improve the mechanical characteristics of composite materials.

From the point of view of physical mesomechanics, the design of nanostructured materials will make it possible to obtain new objects with a multilevel organization, which is necessary for a more correct approach to the study of structural transformation at the nanoscale level.

The development of new approaches to the formation of composites with two or more reinforcing modifiers is an important trend in modern materials science, which makes it possible to improve a whole range of functional properties and, at the same time, reduce the total cost of the material. The review shows that the combined use of two reinforcing phases (CNT and TiC with a dispersion of 150 nm) makes it possible to neutralize the negative qualities of the reinforcing phase and obtain a composite material based on an aluminum matrix, which has higher strength characteristics while maintaining the plasticity of the composite.

In addition, for directed control of the composition of the structure and properties of composites, combined technological approaches are being developed using the methods of powder metallurgy and surface modification. This is one of the promising technological directions in the creation of composites.

For a better understanding of the direction of the development possibilities of composite materials with carbon reinforcing structures, the review presents microscopic structural modeling methods that can be used to reproduce the influence of model size, interfacial behavior, CNT volume fraction and layered structures on the mechanical behavior of CNT–Al composites in order to understand the mechanisms of hardening and deformation of CNT–Al composites. MMC simulation results show that the improved mechanical properties of CNT–Al composites can be attributed to three factors: CNT hardening, matrix grain refinement, and layered architecture.

Author Contributions: Conceptualization, E.G.Z. and V.M.S.; methodology, Y.V.S.; writing—original draft preparation, E.G.Z., V.M.S., and A.Y.A.; writing—review and editing, E.G.Z., P.M.K., B.N.S., and N.F.M.; supervision, E.G.Z.; funding acquisition, E.G.Z. All authors have read and agreed to the published version of the manuscript.

Funding: The research was conducted with financial support from the Russian Science Foundation grant (project No. 20-11-20083).

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: Not applicable.

Acknowledgments: Scientific research was performed at the Research parks of St. Petersburg State University: the RC «Nanotechnologies», the RC “X-ray Diffraction research methods”, and «Center for Innovative Technologies of Composite Nanomaterials».

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Chawla, K.K. *Composite Materials: Science and Engineering*, 3rd ed.; Springer Science + Business Media: New York, NY, USA, 2013; p. 542, ISBN 978-0-387-74364-6.
2. Kumar, V.M.; Venkatesha, C.V. Effect of ceramic reinforcement on mechanical properties of aluminum matrix composites produced by stir casting process. *Mater. Today Proc.* **2018**, *5*, 2466–2471.
3. Kablov, E.N. Innovative developments of FSUE "VIAM" of the State Research Center of the Russian Federation on the implementation of "Strategic directions for the development of materials and technologies of their processing for the period up to 2030. *Aviat. Mater. Technol.* **2015**, *34*, 3–33.
4. Yufeng, W.; Gap-Yong, K.; Alan, M.R. Mechanical alloying of carbon nanotube and Al6061 powder for metal matrix composites. *Mater. Sci. Eng. A* **2012**, *532*, 558–566.
5. Bakshi, S.R.; Lahiri, D.; Argaval, A. Carbon nanotube reinforced metal matrix composites—a review. *Int. Mater. Rev.* **2013**, *55*, 41–64.
6. Matthews, F.L.; Rawlings, R.D. *Composite Materials: Engineering and Science*; CRS Press: Boca Raton, FL, USA, 1999; ISBN 0-8493-0621-3.
7. Bayda, S.; Adeel, M.; Tuccinardi, T.; Cordani, M.; Rizzolio, F. The History of Nanoscience and Nanotechnology: From Chemical–Physical Applications to Nanomedicine. *Molecules* **2020**, *25*, 112.
8. Rogov, V.A. *Technology of structural materials. Nanotechnologies*, 2nd ed.; Urait: Moscow, Russia, 2022; p. 190.
9. Chang, L.; Zhang, Z.; Ye, L.; Friedrich, K. Tribological properties of high temperature resistant polymer composites with fine particles. *Tribol. Int.* **2007**, *40*, 1170–1178.
10. Liao, X.Z.; Serquis, A.; Jia, Q.; Peterson, D.; Zhu, Y.; Xu, H. Effect of catalyst composition on carbon nanotube growth. *Appl. Phys. Lett.* **2003**, *82*, 2694–2696.
11. Gleiter, H. Nanostructured materials. Basic Concepts and Microstructure. *Acta Mater.* **2000**, *48*, 1–29.
12. Suzdalev, I.P. *Nanotechnology: Physico-Chemistry of Nanoclusters, Nanostructures and Nanomaterials*; ComKniga: Moscow, Russia, 2006; p. 592.
13. Agarwal, A.; Bakshi, S.R.; Lahiri, D. *Carbon Nanotubes: Reinforced Metal Matrix Composites*; CRC Press: Boca Raton, FL, USA, 2011; 305p.
14. Nolan, P.E.; Schabel, M.J.; Lynch, D.C.; Cutler, A.H. Hydrogen control of carbon deposit morphology. *Carbon* **1995**, *33*, 79–85.
15. Romero, A.; Garrido, A.; Nieto-Márquez, A.; Sánchez, P.; de Lucas, A.; Valverde, J.L. Synthesis and structural characteristics of highly graphitized carbon nanofibers produced from the catalytic decomposition of ethylene: Influence of the active metal (Co, Ni, Fe) and the zeolite type support. *Microporous Mesoporous Mater.* **2008**, *110*, 318–329.
16. Verfssimo, C.; Moshkalyo, S.A.; Ramos, A.C.S.; Gonçalves, J.L.; Alves, O.L.; Swart, J.W. Different Carbon Nanostructured Materials Obtained in Catalytic Chemical Vapor Deposition. *J. Braz. Chem. Soc.* **2006**, *17*, 1124–1132.

17. Osawa, E. *Perspectives of Fullerene Nanotechnology*, 1st ed.; Springer Dordrecht: Dordrecht, The Netherlands, 2002; ISBN 978-0-306-47621-1.
18. Delgado, J.L.; Herranz, M.A.; Martin, N. The nano-forms of carbon. *J. Mater. Chem.* **2008**, *18*, 1417–1426.
19. Neitzel, I.; Mochalin, V.; Bares, J.A.; Carpick, R.W.; Erdemir, A.; Gogotsi, Y. Tribological properties of nanodiamond-epoxy composites. *Tribol. Lett.* **2012**, *47*, 195–202.
20. Geim, A.K.; Grigorieva, I.V. Van der Waals heterostructures. *Nature* **2013**, *499*, 419–425.
21. Korusenko, P.M.; Nesov, S.N.; Iurchenkova, A.A.; Fedorovskaya, E.O.; Bolotov, V.V.; Povoroznyuk, S.N.; Smirnov, D.A.; Vinogradov, A.S. Comparative Study of the Structural Features and Electrochemical Properties of Nitrogen-Containing Multi-Walled Carbon Nanotubes after Ion-Beam Irradiation and Hydrochloric Acid Treatment. *Nanomaterials* **2021**, *11*, 2163.
22. Kis, A.; Csányi, G.; Salvétat, J.-P.; Lee, Thien-Nga; Couteau, E.; Kulik, A.J.; Benoit, W.; Brugger, J.; Forró, L. Reinforcement of single-walled carbon nanotube bundles by intertube bridging. *Nat. Mater.* **2004**, *3*, 153–157.
23. Trofimov, N.A. Technology based on nanotubes: Industrial application and product market. *Sci. Abroad.* **2012**, *3*, 2–23.
24. Lau, K. Interfacial bonding characteristics of nanotube/polymer. *Chem. Phys. Lett.* **2003**, *370*, 399–405.
25. Zhang, H. Introduction: 2D Materials Chemistry. *Chem. Rev.* **2018**, *118*, 6089–6090.
26. Li, F.; Jiang, X.; Zhao, J.; Zhang, S. Graphene oxide: A promising Nanomaterial for energy and environmental applications. *Nano Energy* **2015**, *16*, 488–515.
27. Yao, X.; Niu, X.; Ma, K.; Huang, P.; Grothe, J.; Kaskel, S.; Zhu, Y. Graphene Quantum Dots-Capped Magnetic Mesoporous Silica Nanoparticles as a Multifunctional Platform for Controlled Drug Delivery. Magnetic Hyperthermia and Photothermal Therapy, *Small* **2017**, *13*, 1602225.
28. Britnell, L.; Gorbachev, R.V.; Jalil, R.; Belle, B.D.; Schedin, F.; Mishchenko, A.; Georgiou, T.; Katsnelson, M.I.; Eaves, L.; Morozov, S.V.; et al. Field-Effect Tunneling Transistor Based on Vertical Graphene Heterostructures. *Science* **2012**, *335*, 947–950.
29. Britnell, L.; Gorbachev, R.V.; Geim, A.K.; Ponomarenko, L.A.; Mishchenko, A.; Greenaway, M.T.; Fromhold, T.M.; Novoselov, K.S.; Eaves, L. Resonant tunnelling and negative differential conductance in graphene transistors. *Nat. Commun.* **2013**, *4*, 1794.
30. Singh, A.; Shishodia, M.S. Graphene vs. silica coated refractory nitrides based core-shell nanoparticles for nanoplasmonic sensing. *Physica E Low Dimens. Syst. Nanostruct.* **2020**, *124*, 114288.
31. Boehm, H.P.; Clauss, A.; Fischer, G.O.; Hofmann, U. The Adsorption Behavior of Very Thin Carbon Films. *Z. Anorg. Allg. Chem.* **1962**, *316*, 119–127.
32. Novoselov, K.S.; Geim, A.K.; Morozov, S.V.; Jiang, D.; Zhang, Y.; Dubonos, S.V.; Grigorieva, I.V.; Firsov, A.A. Electric field effect in atomically thin carbon films. *Science* **2004**, *306*, 666–669.
33. Shang, L.; Bian, T.; Zhang, B.; Zhang, D.; Wu, L.Z.; Tung, C.H.; Yin, Y.; Zhang, T. Graphene-supported ultrafine metal nanoparticles encapsulated by mesoporous silica: Robust catalysts for oxidation and reduction reactions. *Angew. Chem. Int. Ed. Engl.* **2014**, *53*, 250–254.
34. Bhuyan, M.d.S.A.; Uddin, M.d.N.; Islam, M.d.M.; Bipasha, F.A.; Hossain, S.S. Synthesis of graphene. *Int. Nano Lett.* **2016**, *6*, 65–83.
35. Britnell, L.; Ribeiro, R.M.; Eckmann, A.; Jalil, R.; Belle, B.D.; Mishchenko, A.; Kim, Y.-J.; Gorbachev, R.V.; Georgiou, T.; Morozov, S.V.; et al. Strong Light Matter Interactions in Heterostructures of Atomically Thin Films. *Science* **2013**, *340*, 1311–1314.
36. Stoller, M.D.; Park, S.; Zhu, Y.; An, J.; Ruoff, R.S. Graphene-Based Ultracapacitors. *Nano Lett.* **2008**, *8*, 3498–3502.
37. Gong, Y.; Lin, J.; Wang, X.; Shi, G.; Lei, S.; Lin, Z.; Zou, X.; Ye, G.; Vajtai, R.; Yakobson, B.I.; et al. Vertical and in-plane heterostructures from WS₂/MoS₂ monolayers. *Nat. Mater.* **2014**, *13*, 1135–1142.
38. Eizenberg, M.; Blakely, J.M. Carbon interaction with nickel surfaces: Monolayer formation and structural stability. *J. Chem. Phys.* **1979**, *71*, 3467–3477.
39. Lang, B.A. LEED study of the deposition of carbon on platinum crystal surfaces. *Surf. Sci.* **1975**, *53*, 317–329.
40. Morozov, S.V.; Novoselov, K.S.; Katsnelson, M.I.; Schedin, F.; Elias, D.C.; Jaszczak, J.A.; Geim, A.K. Giant Intrinsic Carrier Mobilities in Graphene and Its Bilayer. *Phys. Rev. Lett.* **2008**, *100*, 016602.
41. Lee, C.; Wei, X.D.; Kysar, J.W.; Hone, J. Measurement of the Elastic Properties and Intrinsic Strength of Monolayer Graphene. *Science* **2008**, *321*, 385–3858.
42. Balandin, A.A.; Ghosh, S.; Bao, W.Z.; Calizo, I.; Teweldebrhan, D.; Miao, F.; Lau, C.N. Superior Thermal Conductivity of Single-Layer Graphene. *Nano Lett.* **2008**, *8*, 902–907.
43. Ghosh, S.; Calizo, I.; Teweldebrhan, D.; Pokatilov, E.P.; Nika, D.L.; Balandin, A.A.; Bao, W.; Miao, F.; Lau, C.N. Extremely high thermal conductivity of graphene: Prospects for thermal management applications in nanoelectronic circuits. *Appl. Phys. Lett.* **2008**, *92*, 151911.
44. Feng, W.; Long, P.; Feng, Y.; Li, Y. Two-dimensional fluorinated graphene: Synthesis, structures, properties and applications. *Adv. Sci.* **2016**, *3*, 1500413.
45. Ponomarenko, L.A.; Geim, A.K.; Zhukov, A.A.; Jalil, R.; Morozov, S.V.; Novoselov, K.S.; Grigorieva, I.V.; Hill, E.H.; Cheianov, V.V.; Fal'ko, V.I.; et al. Tunable metal-insulator transition in double-layer graphene heterostructures. *Nat. Phys.* **2011**, *7*, 958–961.
46. Eizenberg, M.; Blakely, J.M. Carbon monolayer phase condensation on Ni(111). *Surf. Sci.* **1979**, *82*, 228–236.
47. Jirickova, A.; Jankovsky, O.; Sofer, Z.; Sedmidubsky, D. Synthesis and Applications of Graphene Oxide. *Materials* **2022**, *15*, 920.
48. Kang, J.; Tongay, S.; Zhou, J.; Li, J.; Wu, J. Band offsets and heterostructures of two-dimensional semiconductors. *Appl. Phys. Lett.* **2013**, *102*, 012111.

49. Vincent, T.; Liang, J.; Singh, S.; Castanon, E.G.; Zhang, X.; McCreary, A.; Jariwala, D.; Kazakova, O.; Al Balushi, Z.Y. Opportunities in electrically tunable 2D materials beyond graphene: Recent progress and future outlook. *Appl. Phys. Rev.* **2021**, *8*, 041320.
50. Novoselov, K.S. Graphene: Materials in the Flatland. *Int. J. Mod. Phys. B* **2011**, *25*, 4081–4106.
51. Datye, I.M.; Gabourie, A.J.; English, C.D.; Smithe, K.K.H.; McClellan, C.J.; Wang, N.C.; Pop, E. Reduction of hysteresis in MoS₂ transistors using pulsed voltage measurements. *2D Mater.* **2019**, *6*, 011004.
52. Antonova, I.V. Vertical heterostructures based on graphene and other 2D materials. *Semiconductors* **2016**, *50*, 66–82.
53. Fiori, G.; Bruzzone, S.; Iannaccone, G. Very Large Current Modulation in Vertical Heterostructure Graphene/hBN Transistors. *IEEE Trans. Electron Devices* **2013**, *60*, 268–273.
54. Stylianakis, M.M.; Viskadourous, G.; Polyzoidis, C.; Veisakis, G.; Kenanakis, G.; Kornilios, N.; Petridis, K.; Kymakis, E. Updating the Role of Reduced Graphene Oxide Ink on Field Emission Devices in Synergy with Charge Transfer Materials. *Nanomaterials* **2019**, *9*, 137.
55. Fiori, G.; Betti, A.; Bruzzone, S.; Iannaccone, G. Lateral Graphene–hBCN Heterostructures as a Platform for Fully Two-Dimensional Transistors. *ACS Nano* **2012**, *6*, 2642–2648.
56. Paussa, A.; Fiori, G.; Palestri, P.; Geromel, M.; Esseni, D.; Iannaccone, G.; Selmi, L. Simulation of the Performance of Graphene FETs With a Semiclassical Model, Including Band-to-Band Tunneling. *IEEE Trans. Electron Devices* **2014**, *61*, 1567–1574.
57. Georgakilas, V.; Otyepka, M.; Bourlinos, A.B.; Chandra, V.; Kim, N.; Kemp, K.Ch.; Hobza, P.; Zboril, R.; Kim, K.S. Functionalization of Graphene: Covalent and Non-Covalent Approaches, Derivatives and Applications. *Chem. Rev.* **2012**, *112*, 6156–6214.
58. Zemtsova, E.G.; Yurchuk, D.V.; Smirnov, V.M. Creation of heterogeneity on the basis of carbide nanostructures in the volume of metal (iron) matrix for regulation of mechanical properties. *Mater. Phys. Mech.* **2013**, *18*, 42–52.
59. Pham, X.H.; Hahm, E.; Kim, H.M.; Son, B.S.; Jo, A.; An, J.; Tran Thi, T.A.; Nguyen, D.Q.; Jun, B.H. Silica-Coated Magnetic Iron Oxide Nanoparticles Grafted onto Graphene Oxide for Protein Isolation. *Nanomaterials* **2020**, *10*, 117.
60. An, X.; Simmons, T.; Shah, R.; Wolfe, Ch.; Lewis, K.M.; Washington, M.; Nayak, S.K. Talapatca Si, Ka Si Stable Aqueous Dispersions of Noncovalently Functionalized Graphene from Graphite and their Multifunctional High-Performance Applications. *Nano Lett.* **2010**, *10*, 4295–4301.
61. Tolochko, O.V.; Koltsova, T.S.; Bobrynina, E.V.; Rudskoy, A.I.; Zemtsova, E.G.; Kirichenko, S.O.; Smirnov, V.M. Conditions for Production of Composite Material Based on Aluminum and Carbon Nanofibers and Its Physic-Mechanical Properties. *Nanomaterials* **2019**, *9*, 550.
62. Casati, R.; Vedani, M. Metal matrix composites reinforced by nano-particles. a review. *Metals* **2014**, *4*, 65–83.
63. Zemtsova, E.G.; Morozov, P.E.; Semenov, B.N.; Morozov, N.F.; Smirnov, V.M. Chemical Preparation of the Surface of a Porous Nickel Matrix for Conducting the Synthesis of TiC Nanolayer. *Russ. J. Gen. Chem.* **2019**, *89*, 169–171.
64. Zemtsova, E.G.; Yurchuk, D.V.; Morozov, P.E.; Kudymov, V.K.; Smirnov, V.M. Features of the synthesis of the dispersed TiC phase with nickel nanostructures on the surface to create an aluminum-based metal composite. *Nanomaterials* **2021**, *11*, 2499.
65. Robertson, D.H.; Brenner, D.W.; Mintmire, J.W. Progress on mechanics of carbon nanotubes and derived materials. *Phys. Rev. B* **1992**, *45*, 12592.
66. Sanchez-Portal, D.; Artacho, E.; Soler, J.M.; Rubio, A.; Ordejón, P. Ab initio structural, elastic and vibrational properties of carbon nanotubes. *Phys. Rev. B.* **1999**, *59*, 12678.
67. Suk, M.E. Effect of the Nanotube Radius and the Volume Fraction on the Mechanical Properties of Carbon Nanotube-Reinforced Aluminum Metal Matrix Composites. *Molecules* **2021**, *26*, 3947.
68. Melezhik, A.V.; Romantsova, I.V.; Dyachkova, T.P.; Bychkov, O.N.; Shlykova, A.; Smykov, M.A.; Tkachev, A.; Golovin, Y. Effect of the Matrix Composition on Activity of Metal Oxide Catalysts in CVD Syntesis of Carbon Nanotubes. *Russ. J. Appl. Chem.* **2012**, *85*, 782–787.
69. Nurazzi, N.M.; Sabaruddin, F.A.; Harussani, M.M.; Kamarudin, S.H.; Rayung, M.; Asyraf, M.R.M.; Aisyah, H.A.; Norrrahim, M.N.F.; Ilyas, R.A.; Abdullah, N.; et al. Mechanical Performance and Applications of CNTs Reinforced Polymer Composites—A Review. *Nanomaterials* **2021**, *11*, 2186.
70. Khandoker, N.; Hawkins, S.C.; Ibrahim, R.; Huynh, C.P.; Deng, F. Tensile Strength of Spinnable Multiwall Carbon Nanotubes. *Procedia Eng.* **2011**, *10*, 2572–2578.
71. Fan, M.; Zhao, F.; Liu, Y.; Yin, S.; Peng, S.; Zhang, Z. Zinc Matrix Composites Reinforced with Partially Unzipped Carbon Nanotubes as Biodegradable Implant Materials. *Crystals* **2022**, *12*, 1110.
72. Rukhov, A.V.; Dyachkova, T.P.; Tugolukov, E.; Besperstova, G. Macrokinetics of carbon nanotubes synthesis by the chemical vapor deposition method. *AIP Conf. Proc.* **2017**, *1899*, 020019.
73. Mwesigye, A.; Yilmaz, İ.H.; Meyer, J.P. Numerical analysis of the thermal and thermodynamic performance of a parabolic trough solar collector using SWCNTs-Therminol®VP-1 nanofluid. *Renew. Energy* **2018**, *119*, 844–862.
74. Angadi, M.A.; Watanabe, T.; Bodapati, A.; Xiao, X.; Auciello, O.; Carlisle, J.A.; Eastman, J.A.; Keblinski, P.; Schelling, P.K.; Phillpot, S.R. Thermal transport and grain boundary conductance in ultrananocrystalline diamond thin films. *J. Appl. Phys.* **2006**, *99*, 114301.
75. So, K.P.; Jeong, J.C.; Park, J.G.; Park, H.K.; Choi, Y.H.; Noh, D.H.; Keum, D.H.; Jeong, H.Y.; Biswas, C.; Hong, C.H.; et al. SiC formation on carbon nanotube surface for improving wettability with aluminum. *Compos. Sci. Technol.* **2013**, *74*, 6–13.
76. He, C.; Zhao, N.; Shi, C.; Du, X.; Li, J.; Li, H.; Cui, Q. An Approach to Obtaining Homogeneously Dispersed Carbon Nanotubes in Al Powders for Preparing Reinforced Al-Matrix Composites. *Adv. Mater.* **2007**, *19*, 1128–1132.
77. Rakov, E.G. *Nanotubes and Fullerenes*, 1st ed.; Logos: Moscow, Russia, 2006; ISBN 5-98699-0009-9.

78. Moseenkov, S.I.; Kuznetsov, V.L.; Zavorin, A.V.; Golubtsov, G.V.; Ishchenko, A.V.; Serkova, A.N.; Korovin, E.Y.; Suslyayev, V.I.; Sergeenko, D.I.; Velikanov, D.A. Electrophysical properties of composites based on polyethylene modified with multi-walled carbon nanotubes with high content of Fe–Co-catalyst. *Russ. J. Appl. Chem.* **2020**, *93*, 586–594.
79. Rakov, E.G. Methods for preparation of carbon nanotubes. *Russ. Chem. Rev.* **2000**, *69*, 35–52.
80. Klimov, E.S.; Buzaeva, M.V.; Davydova, O.A.; Makarova, I.A.; Svetukhin, V.V.; Kozlov, D.V.; Pchelintseva, E.S.; Bunakov, N.A. Some aspects of the synthesis of multi-walled carbon nanotubes by chemical vapor deposition and characteristics of the resulting material. *Russ. J. Appl. Chem.* **2014**, *87*, 1128–1132.
81. Ob'edkov, A.M.; Kaverin, B.S.; Gusev, S.A.; Ezerskii, A.B.; Semenov, N.M.; Zaytsev, A.A.; Egorov, V.A.; Domrachev, G.A. MOCVD modification of the surface of multiwalled carbon nanotubes to impart to them necessary physicochemical properties. *J. Synch. Investig.* **2009**, *3*, 61–66.
82. Sun, Y.; Chen, Q. Diameter dependent strength of carbon nanotube reinforced composite. *Appl. Phys. Lett.* **2009**, *95*, 021901–021903.
83. Bolotov, V.V.; Kan, V.E.; Biryukov, M.Y.; Knyazev, E.V.; Shelyagin, R.V.; Korusenko, P.M.; Nesov, S.N.; Sten'kin, Y.A. Origin of the low-frequency band in Raman spectra of multi-walled carbon nanotubes synthesized by the CVD method. *Phys. Solid State* **2013**, *55*, 1459–1462.
84. Spitalsky, Z.; Tasis, D.; Papagelis, K.; Galiotis, C. Carbon nanotube–polymer composites: Chemistry, processing, mechanical and electrical properties. *Prog. Polym. Sci.* **2010**, *35*, 357–401.
85. Potschke, P.; Fornes, T.D.; Paul, D.R. Rheological behaviour of multiwalled carbon nanotubes/polycarbonate composites. *Polymer* **2002**, *43*, 3247–3255.
86. Nesov, S.N.; Korusenko, P.M.; Sachkov, V.A.; Bolotov, V.V.; Povoroznyuk, S.N. Effects of preliminary ion beam treatment of carbon nanotubes on structures of interfaces in MOx/multi-walled carbon nanotube (M =Ti,Sn) composites: Experimental and theoretical study. *J. Phys. Chem. Solids* **2022**, *169*, 110831.
87. Bolotov, V.V.; Nesov, S.N.; Korusenko, P.M.; Povoroznyuk, S.N. Transformation of the electronic structure of the SnO₂ – x /MWCNT nanocomposite under high-vacuum annealing conditions. *Phys. Solid State* **2014**, *56*, 1899–1903.
88. Jiang, L.; Li, Z.; Fan, G.; Cao, L.; Zhang, D. The use of flake powder metallurgy to produce carbon nanotube (CNT)/aluminum composites with a homogenous CNT distribution. *Carbon* **2012**, *50*, 1993–1998.
89. Liu, Z.Y.; Xiao, B.L.; Wang, W.G.; Ma, Z.Y. Developing high-performance aluminum matrix composites with directionally aligned carbon nanotubes by combining friction stir processing and subsequent rolling. *Carbon* **2013**, *62*, 35–42.
90. Zhang, T.; Kumari, L.; Du, G.H.; Li, W.Z.; Wang, Q.W.; Balani, K.; Agarwal, A. Mechanical properties of carbon nanotube-alumina nanocomposites synthesized by chemical vapor deposition and spark plasma sintering. *Compos. Part A Appl. Sci. Manuf.* **2009**, *40*, 86–93.
91. Zhu, X.; Zhao, Y.-G.; Wu, M.; Wang, H.-Y.; Jiang, Q.-C. Fabrication of 2014 aluminum matrix composites reinforced with untreated and carboxyl-functionalized carbon nanotubes. *J. Alloys Compd.* **2016**, *674*, 145–152.
92. Abu Al-Rub, R.K.; Ashour, A.I.; Tyson, B.M. On the Aspect Ratio Effect of Multi-Walled Carbon Nanotube Reinforcements on the Mechanical Properties of Cementitious Nanocomposites. *Constr. Build Mater.* **2012**, *35*, 647–655.
93. Arsecularatne, J.A.; Zhang, L.C. Carbon Nanotube Reinforced Ceramic Composites and their Performance. *Recent Pat. Nanotechnol.* **2007**, *1*, 176–185.
94. Klimov, E.S.; Buzaeva, M.V.; Davydova, O.A.; Isaev, A.V.; Nishchev, K.N.; Pynenkov, A.A.; Kalashnikov, E.G.; Fomin, A.N.; Svetukhin, V.V. Changing the surface and properties of multi-walled carbon nanotubes during physico-chemical modification. *Russ. J. Appl. Chem.* **2015**, *88*, 1105–1110.
95. Datsyuk, V.; Kalyva, M.; Papagelis, K.; Parthenios, J.; Tasis, D.; Siokou, A.; Kallitsis, I.; Galiotis, C. Chemical Oxidation of Multiwalled Carbon Nanotubes. *Carbon* **2008**, *46*, 833–840.
96. Mazov, I.; Kuznetsov, V.L.; Simonova, I.A.; Stadnichenko, A.I.; Ishchenko, A.V.; Romanenko, A.I.; Tkachev, E.N.; Anikeeva, O.B. Oxidation Behavior of Multiwall Carbon Nanotubes with Different Diameters and Morphology. *Appl. Surf. Sci.* **2012**, *258*, 6272–6280.
97. Kobets, A.A.; Iurchenkova, A.A.; Asanov, I.P.; Okotrub, A.V.; Fedorovskaya, E.O. Redox Processes in Reduced Graphite Oxide Decorated by Carboxyl Functional Groups. *Phys. Status Solidi B* **2019**, *256*, 1800700.
98. Rasheed, A.; Howe, J.Y.; Dadmun, M.D.; Britt, P.F. The Efficiency of the Oxidation of Carbon Nanofibers with Various Oxidizing Agents. *Carbon* **2007**, *45*, 1072–1080.
99. Worsley, K.A.; Kalinina, I.; Bekyarova, E.; Haddon, R.C. Functionalization and Dissolution of Nitric Acid Treated Single-Walled Carbon Nanotubes. *J. Am. Chem. Soc.* **2009**, *131*, 18153–18158.
100. Deng, C.F.; Wang, D.Z.; Zhang, X.X.; Ma, Y.X. Damping Characteristics of Carbon Nanotube Reinforced Aluminum Composite. *Mater. Lett.* **2007**, *61*, 3229–3231.
101. Jafari, M.; Abbasi, M.H.; Enayati, M.H.; Karimzadeh, F. Mechanical Properties of Nanostructured Al₂₀₂₄–MWCNT Composite Prepared by Optimized Mechanical Milling and Hot Pressing Methods. *Adv. Powder Technol.* **2012**, *23*, 205–210.
102. Rino, J.J.; Chandramohan, D.; Sucitharan, K.S. An overview on development of aluminium metal matrix composites with hybrid reinforcement. *IJSR* **2012**, *1*, 196–203.
103. Song, S.; Billah, M.; Zhou, Q.; Ren, L.; Zheng, L.; Chen, Q.; Bai, Y. Study on Plastic Strengthening Mechanisms of Aluminum Matrix Nano-Composites Reinforced by Nickel Coated CNTs. *Compos. Interfaces* **2020**, *28*, 1015–1036.

104. Kondoh, K.; Threrujirapapong, T.; Imai, H.; Umeda, J.; Fugetsu, B. Characteristics of powder metallurgy pure titanium matrix composite reinforced with multi-wall carbon nanotubes. *Compos. Sci. Technol.* **2009**, *69*, 1077–1081.
105. Saravanan, C.; Subramanian, K.; Krishnan, V.A.; Narayanan, R.S. Effect of particulate reinforced aluminium metal matrix composite—a review. *Mech. Mech. Eng.* **2015**, *19*, 23–30.
106. Kwon, H.; Estili, M.; Takagi, K.; Miyazaki, T.; Kawasaki, A. Combination of hot extrusion and spark plasma sintering or producing carbon nanotube reinforced aluminum matrix composites. *Carbon* **2009**, *47*, 570–577.
107. Maxwell, A.J. Electronic and geometric structure of C60 and Al 111 and Al 110. *Phys. Rev. B.* **1998**, *57*, 7312–7326.
108. Kim, K.T.; Cha, S.I.; Gemming, T. The role of interfacial oxygen atoms in the enhanced mechanical properties of carbon nanotube reinforced metal matrix nanocomposites. *Small* **2008**, *4*, 1936–1940.
109. Park, M.; Kim, B.-H.; Kim, S. Improved binding between copper and carbon nanotubes in a composite using oxygen-containing functional groups. *Carbon* **2011**, *49*, 811–818.
110. Bittencourt, C.; Ke, X.; Tendeloo, G.V.; Thiess, S.; Drube, W.; Ghijsen, J.; Ewels, C.P. Study of the interaction between copper and carbon nanotubes. *Chem. Phys. Lett.* **2012**, *535*, 80–83.
111. Katin, K.P.; Kaya, S.; Maslov, M.M. Graphene nanoflakes and fullerenes doped with aluminum: Features of Al-C interaction and adsorption characteristics of carbon shell. *Lett. Mater.* **2022**, *12*, 148–152.
112. Aditya, I.D.; Matsunaka, D.; Shibutani, Y.; Yamamoto, G. First-principles study of interfacial interaction between carbon nanotube and Al₂O₃(0001). *J. Appl. Phys.* **2017**, *121*, 025304.
113. Deng, C.F.; Wang, D.Z.; Zhang, X.X.; Li, A.B. Processing and properties of carbon nanotubes reinforced aluminum composites. *Mater. Sci. Eng. A.* **2007**, *444*, 138–145.
114. Ci, L.; Ryu, Z.; Yun Jin-Phillipp, N.; Rühle, M. Investigation of the interfacial reaction between multi-walled carbon nanotubes and aluminum. *Acta Mater.* **2006**, *54*, 5367–5375.
115. Kwon, H.; Kawasaki, A. Chapter 7—Effect of Spark Plasma Sintering in Fabricating Carbon Nanotube Reinforced Aluminum Matrix Composite Materials. In *Advances in Composite Materials for Medicine and Nanotechnology*; Attaf, B., Ed.; IntechOpen Limited: London, UK, 2011; pp. 431–444.
116. Shadakshari, R.; Mahesha, K.; Niranjana, H.B. Carbon Nanotube Reinforced Aluminium Matrix Composites—A Review. *IJIRSET* **2012**, *1*, 206–2013.
117. Zhou, W.; Bang, S.; Kurita, H.; Miyazaki, T.; Fan, Y.; Kawasaki, A. Interface and interfacial reactions in multi-walled carbon nanotube reinforced aluminum matrix composites. *Carbon* **2016**, *96*, 919–928.
118. Rudskoy, A.I.; Koltsova, T.S.; Shakhov, F.M.; Tolochko, O.V.; Mikhailov, V.G. Effect of hot pressing modes on the structure and properties of an ‘aluminum–carbon nanofibers’ composite material. *Met. Sci. Heat Treat.* **2015**, *56*, 525–530.
119. Yang, X.; Liu, E.; Shi, C.; He, C.; Li, J.; Zhao, N.; Kondoh, K. Fabrication of carbon nanotube reinforced Al composites with well-balanced strength and ductility. *J. Alloys Compd.* **2013**, *563*, 216–220.
120. He, C.; Zhao, N.; Shi, C.; Du, X.; Li, J.; Li, H.; Cui, Q. An approach to obtaining homogeneously dispersed carbon nanotubes in Al powders for preparing reinforced Al-matrix composites. *Adv. Mater.* **2007**, *19*, 1128–1132.
121. Liao, J.Z.; Tan, M.J.; Sridhar, I. Spark plasma sintered multi-wall carbon nanotube reinforced aluminum matrix composites. *Mater. Des.* **2009**, *31*, 96–100.
122. Feng, Y.; Yuan, H.L.; Zhang, M. Fabrication and properties of silvermatrix composites reinforced by carbon nanotubes. *Mater. Char.* **2005**, *55*, 211–218.
123. Zhong, R.; Cong, H.; Hou, P. Fabrication of nano-Al based composites reinforced by single-walled carbon nanotubes. *Carbon* **2003**, *41*, 848–851.
124. Liu, Z.Y.; Xu, S.J.; Xiao, B.L.; Xue, P.; Wang, W.G.; Ma, Z.Y. Effect of ball-milling time on mechanical properties of carbon nanotubes reinforced aluminum matrix composites. *Compos. Part A Appl. Sci. Manuf.* **2012**, *43*, 2161–2168.
125. Perez-Bustamante, R.; Gómez-Esparza, C.D.; Estrada-Guel, I.; Miki-Yoshida, M.; Licea-Jiménez, L.; Pérez-García, S.A.; Martínez-Sánchez, R. Microstructural and mechanical characterization of Al–MWCNT composites produced by mechanical milling. *Mater. Sci. Eng. A.* **2009**, *502*, 159–163.
126. Jin-zhi, Liao; Ming-Jen, Tan; Idapalapati, Sridhar. Spark Plasma Sintered Multi-Wall Carbon Nanotube Reinforced Aluminum Matrix Composites. *Mater. Des.* **2010**, *31*, 96–100.
127. Suarez, M.; Fernández, A.; Menéndez, J.L.; Torrecillas, R.; Kessel, H.U.; Henniscke, J.; Kirchner, R.; Kessel, T. Chapter 13—Challenges and Opportunities for Spark Plasma Sintering: A Key Technology for a New Generation of Materials. In *Sintering Applications*; Ertug, B., Ed.; IntechOpen Limited: London, UK, 2013; pp. 319–342.
128. Nisar, A.; Zhang, C.; Boesl, B.; Agarwal, A. Unconventional Materials Processing Using Spark Plasma Sintering. *Ceramics* **2021**, *4*, 20–39.
129. Carneiro, Í.; Fernandes, J.V.; Simões, S. Strengthening Mechanisms of Aluminum Matrix Nanocomposites Reinforced with CNTs Produced by Powder Metallurgy. *Metals* **2021**, *11*, 1711.
130. Bakshi, S.R.; Agarwal, A. An Analysis of the Factors Affecting Strengthening in Carbon Nanotube Reinforced Aluminum Composites. *Carbon* **2011**, *49*, 533–544.
131. Padmavathia, K.R.; Ramakrishnan, R. Tribological Behaviour of Aluminium Hybrid Metal Matrix Composite. *Procedia Eng.* **2014**, *97*, 660–667.
132. Razaq, A.M.; Majid, D.L.; Basheer, U.M.; Aljibori, H.S.S. Research Summary on the Processing, Mechanical and Tribological Properties of Aluminium Matrix Composites as Effected by Fly Ash Reinforcement. *Crystals* **2021**, *11*, 1212.

133. Evdokimov, I.A.; Chernyshova, T.A.; Pivovarov, G.I.; Bykov, P.A.; Ivanov, L.A.; Vaganov, V.E. Tribological behavior of aluminum-matrix composites reinforced with carbon nanostructures. *Inorg. Mater. Appl. Res.* **2014**, *5*, 255–262.
134. Srinivasan, R.; Shivananad, H.K. Studies on Tribological characterization of Carbon Nanotube reinforced with 6061 Aluminium Alloy Metal Matrix Composites coated with Nickel. *Int. J. Appl. Eng. Res.* **2019**, *14*, 3721–3729.
135. Kumar, H.G.P.; Xavior, M.A. Chapter 7—Tribological Aspects of Graphene-Aluminum Nanocomposites. In Book *Graphene Materials-Structure, Properties and Modifications*, 2nd ed.; Kyzas, G.; Mitropoulos, A., Eds.; IntechOpen Limited: London, UK, 2017; pp. 154–173.
136. Nasiri, S.; Wang, K.; Yang, M.; Li, Q.; Zaiser, M. Nickel coated carbon nanotubes in aluminum matrix composites: A multiscale simulation study. *Eur. Phys. J. B* **2019**, *92*, 186.
137. Zhou, X.; Song, S.; Li, L.; Zhang, R. Molecular dynamics simulation for mechanical properties of magnesium matrix composites reinforced with nickel-coated single-walled carbon nanotube. *J. Compos. Mater.* **2016**, *50*, 191–200.
138. Kun, X.; Guopeng, Z.; Hai, H.; Jianjian, Z.; Zhongxia, L.; Bin, C. Investigation of the main strengthening mechanism of carbon nanotube reinforced aluminum composites. *Mater. Sci. Eng. A* **2021**, *804*, 140780.
139. Xu, R.; Tan, Z.; Fan, G.; Ji, G.; Li, Z.; Guo, Q.; Li, Z.; Zhang, D. Microstructure-based modeling on structure-mechanical property relationships in carbon nanotube/aluminum composites. *Int. J. Plasticity* **2019**, *120*, 278–295.
140. Dong, S.; Zhou, J.; Hui, D.; Pang, X.; Wang, Q.; Zhang, S.; Wang, L. Interaction between edge dislocations and amorphous interphase in carbon nanotubes reinforced metal matrix nanocomposites incorporating interface effect. *Int. J. Solids Struct.* **2014**, *51*, 1149–1163.
141. Sahoo, B.P.; Das, D.; Chaubey, A.K. Strengthening mechanisms and modelling of mechanical properties of submicron-TiB₂ particulate reinforced Al 7075 metal matrix composites. *Mater. Sci. Eng. A* **2021**, *825*, 141873.
142. Liu, Z.Y.; Xiao, B.L.; Wang, W.G.; Ma, Z.Y. Modelling of carbon nanotube dispersion and strengthening mechanisms in Al matrix composites prepared by high energy ball milling-powder metallurgy method. *Compos. Part A Appl. Sci. Manuf.* **2017**, *94*, 189–198.
143. Dong, S.; Zhou, J.; Hui, D.; Wang, Y.; Zhang, S. Size dependent strengthening mechanisms in carbon nanotube reinforced metal matrix composites. *Compos. Part A Appl. Sci. Manuf.* **2015**, *68*, 356–364.
144. Chen, B.; Shen, J.; Ye, X.; Jia, L.; Li, S.; Umeda, J.; Takahashi, M.; Kondoh, K. Length Effect of Carbon Nanotubes on the Strengthening Mechanisms in Metal Matrix Composites. *Acta Mater.* **2017**, *140*, 317–325.
145. Zeeshan, B.; Othman, M.; Mazli, M. Recent Progress on the Dispersion and the Strengthening Effect of Carbon Nanotubes and Graphene- Reinforced Metal Nanocomposites: A Review. *Crit Rev Solid State* **2018**, *43*, 1–46.
146. Zhou, M.Y.; Ren, L.B.; Fan, L.L.; Tun, K.S.; Gupta, M.; Zhang, Y.W.X.; Lu, T.H.; Quan, G.F. Achieving ultra-high strength and good ductility in AZ61 alloy composites containing hybrid micron SiC and carbon nanotubes reinforcements. *Mater. Sci. Eng. A* **2019**, *768*, 138447.
147. Choi, B.K.; Yoon, G.H.; Lee, S. Molecular dynamics studies of CNT-reinforced aluminum composites under uniaxial tensile loading. *Compos. Part B-Eng.* **2016**, *91*, 119–125.
148. Meguid, S.A.; Al Jahwari, F. Modeling the pullout test of nanoreinforced metallic matrices using molecular dynamics. *Acta Mech.* **2014**, *225*, 1267–1275.
149. Zhang, J.F.; Zhang, X.X.; Wang, Q.Z.; Xiao, B.L.; Ma, Z.Y. Simulations of deformation and damage processes of SiCp/Al composites during tension. *J. Mater. Sci. Technol.* **2018**, *34*, 627–634.
150. Jagannatham, M.; Chandran, P.; Sankaran, S.; Haridoss, P.; Nayan, N.; Bakshi, S.R. Tensile properties of carbon nanotubes reinforced aluminum matrix composites: A review. *Carbon* **2020**, *160*, 14–44.
151. Ahmadi, M.; Ansari, R.; Hassanzadeh-Aghdam, M.K. Micromechanical analysis of elastic modulus of carbon nanotube-aluminum nanocomposites with random microstructures. *J. Alloys Compd.* **2019**, *779*, 433–439.
152. Pérez, L.; Cabrera, I.; Santiago, A.A.; Vargas, J.; Beltrán, A.; Alfonso, I. Effect of the Al–CNT interlayer on the tensile elastic modulus of Al matrix composites with random dispersion of CNTs. *J. Braz. Soc. Mech. Sci.* **2018**, *40*, 550.
153. Dong, S.; Zhou, J.; Liu, H.; Qi, D. Computational prediction of waviness and orientation effects in carbon nanotube reinforced metal matrix composites. *Comp. Mater. Sci.* **2015**, *101*, 8–15.
154. Su, Y.; Li, Z.; Jiang, L.; Gong, X.; Fan, G.; Zhang, D. Computational structural modeling and mechanical behavior of carbon nanotube reinforced aluminum matrix composites. *Mater. Sci. Eng. A* **2014**, *614*, 273–283.